



Reinforced Concrete Beams Ultimate Strength Design (ACI 318 - 2019)

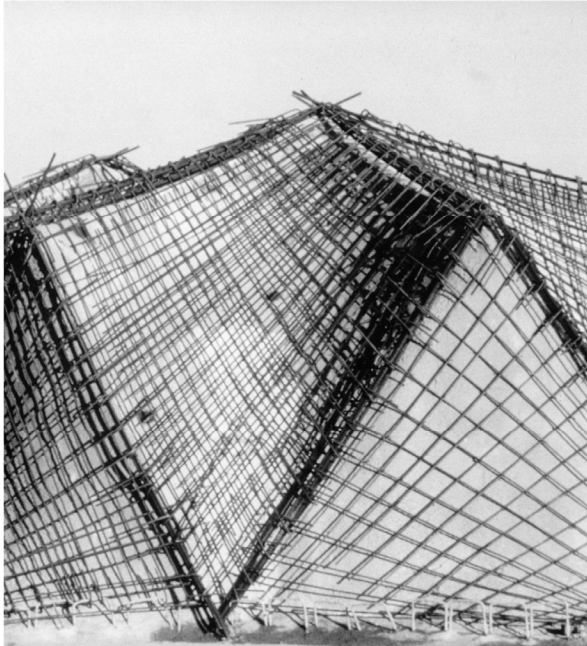

- Flexure in Concrete
- Ultimate Strength Design (LRFD)
- Failure Modes
- Flexure Equations
- Analysis of Rectangular Beams
- Design of Rectangular Beams
- Analysis of Non-rectangular Beams


Flexure

The stress trajectories in this simple beam, show principle tension as solid lines.


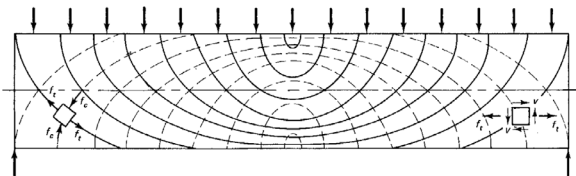


Reinforcement must be placed to resist these tensile forces

In beams continuous over supports, the stress reverses (negative moment). In such areas, tensile steel is on top.

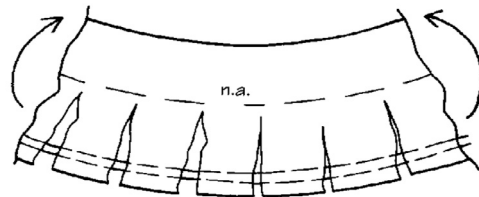

Shear reinforcement is provided by vertical or sloping stirrups.

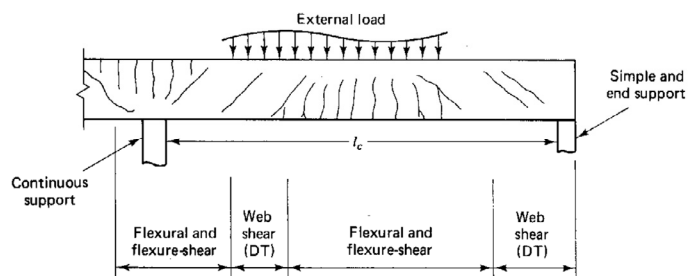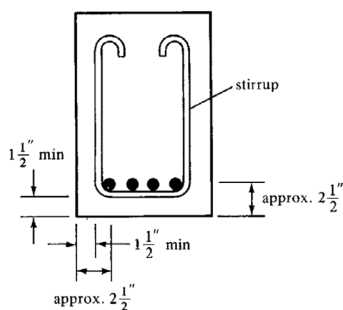

Ultimate Strength – (LRFD)

Nominal Strength \geq Design Strength
(strength of member \geq required by loads)

LRFD uses 2 safety factors: γ and ϕ
 ϕ nominal strength $\geq \gamma$ required strength

γ increases the required strength of the member and is placed on the loads

ϕ reduces the member strength capacity and is placed on the calculated force

Loads increased:

γ Factors: DL=1.2 LL=1.6
U is the required strength
U=1.2DL+1.6LL
(factors from ASCE 7)

Strength reduced:

ϕ Factors: e.g. flexure = 0.9
in tension-controlled beams

Table 21.2.1—Strength reduction factors ϕ

Action or structural element	ϕ	Exceptions
(a) Moment, axial force, or combined moment and axial force	0.65 to 0.90 in accordance with 21.2.2	Near ends of pre-tensioned members where strands are not fully developed, ϕ shall be in accordance with 21.2.3.
(b) Shear	0.75	Additional requirements are given in 21.2.4 for structures designed to resist earthquake effects.
(c) Torsion	0.75	—
(d) Bearing	0.65	—
(e) Post-tensioned anchorage zones	0.85	—
(f) Brackets and corbels	0.75	—
(g) Struts, ties, nodal zones, and bearing areas designed in accordance with strut-and-tie method in Chapter 23	0.75	—
(h) Components of connections of precast members controlled by yielding of steel elements in tension	0.90	—
(i) Plain concrete elements	0.60	—
(j) Anchors in concrete elements	0.45 to 0.75 in accordance with Chapter 17	—

Ultimate Strength – (ACI 318)

Reduced Nominal Strength \geq Factored Load Effects

$$\phi S_n \geq U$$

γ Factored Loads (see ACSE 7)


- 1) 1.4D
- 2) 1.2D + 1.6L + 0.5(Lr or S or R)
- 3) 1.2D + 1.6(Lr or S or R) + (1.0L or 0.5W)
- 4) 1.2D + 1.0W + 1.0L + 0.5(Lr or S or R)
- 5) 1.2D + 1.0E + 1.0L + 0.2S
- 6) 0.9D + 1.0W
- 7) 0.9D + 1.0E

D = service dead loads
L = service live load
Lr = service roof live load
S = snow loads
W = wind loads
R = rainwater loads
E = earthquake loads

Strength Reduction Factors, ϕ

Mn	Flexural ($\epsilon > 0.005$)	0.90
Vn	Shear	0.75
Pn	Compression (spiral)	0.75
Pn	Compression (other)	0.65
Bn	Bearing	0.65
Tn	Torsion	0.75
Nn	Tension	0.90
Combined stress		0.65 to 0.90

ACI 318 21.2.2

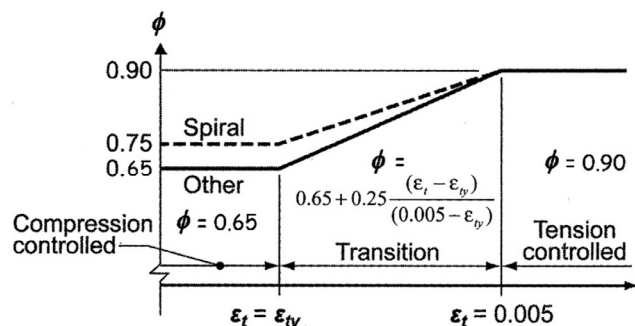

Strength Measurement

- Compressive strength



- 12" x 6" cylinder
- 28 day moist cure
- Ultimate (failure) strength
- Usable strain $\epsilon_{cu} = 0.003$ (ACI 318)

$$f'_c$$

- Tensile strength ASTM C496

- 12" x 6" cylinder
- 28 day moist cure
- Ultimate (failure) strength
- Split cylinder test
- ca. 10% of f'_c
- Neglected in flexure analysis

$$f'_t$$

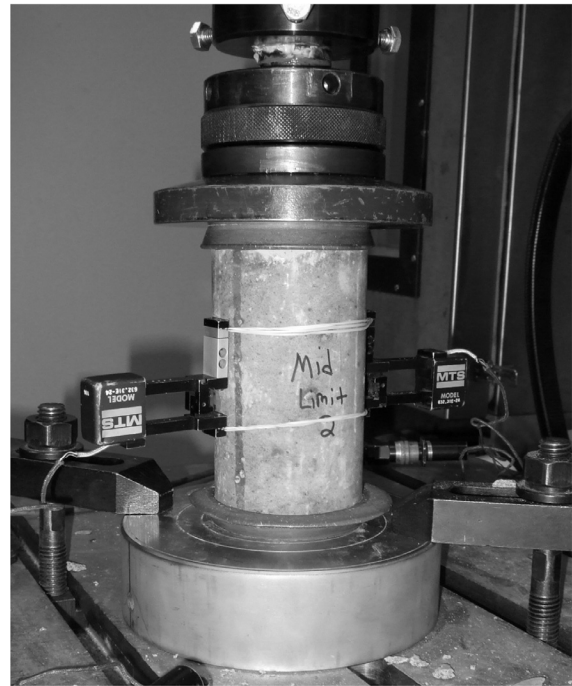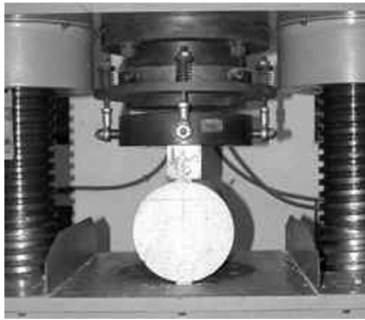

Failure Modes Based on A_s

- **No Reinforcing**

- Less than $A_{s \text{ min}}$
- Brittle failure

$$\rho = \frac{A_s}{bd}$$

$A_{s, \text{min}}$:
greater of a and b

- **Reinforcing < balance (use this)**

- Steel yields before concrete fails
- ductile failure
- ($\sim A_{s \text{ min}}$) $0.06 \geq \epsilon_t \geq 0.004$ ($A_{s \text{ max}}$)
- $\epsilon_t \geq 0.005$ for tension controlled

(a) $\frac{3\sqrt{f'_c}}{f_y} b_w d$

(b) $\frac{200}{f_y} b_w d$

$$A_{s, \text{max}} \text{ when } \epsilon_t = 0.004$$

- **Reinforcing = balance**

- Concrete fails just as steel yields
- ϵ_t at balance = 0.00207 for Gr 60

$$\rho_{\text{bal}} = \left(\frac{0.85\beta_1 f'_c}{f_y} \right) \left(\frac{87000}{87000 + f_y} \right)$$

- **Reinforcing > balance**

- Concrete fails before steel yields
- Low ductility
- Sudden failure

$$A_s > A_{s, \text{max}} \quad \text{SuddenDeath!!}$$



ACI Stress Block

β_1 is a factor to account for the non-linear shape of the compression stress block.

$$a = \beta_1 c$$


psi

f'_c	β_1
0	0.85
1000	0.85
2000	0.85
3000	0.85
4000	0.85
5000	0.8
6000	0.75
7000	0.7
8000	0.65
9000	0.65
10000	0.65

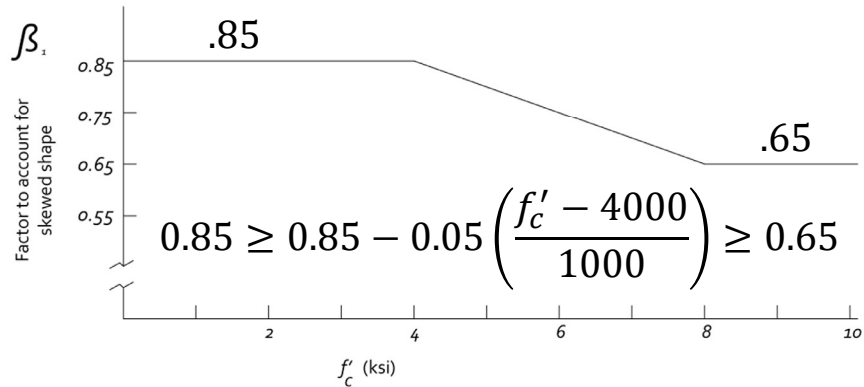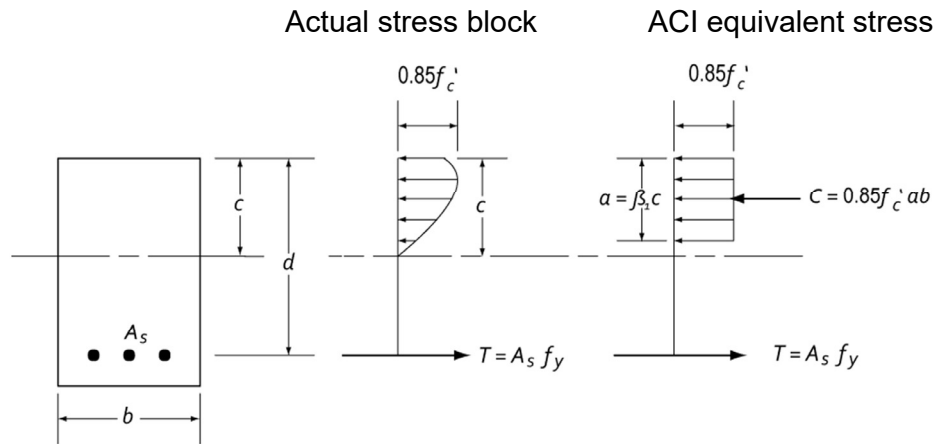

Flexure Equations

strain ACI equivalent stress block

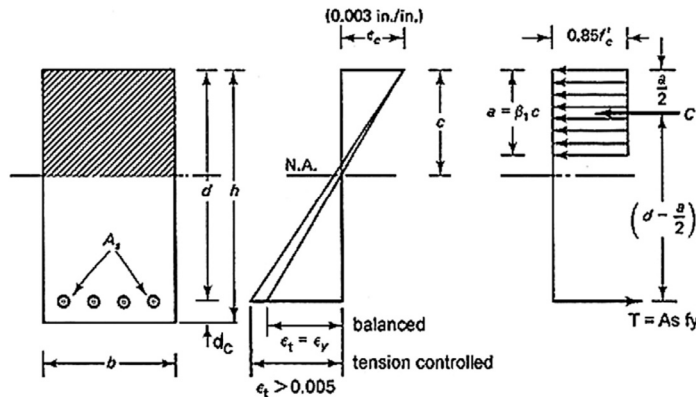

$$C = T$$

$$0.85f'_c ab = A_s f_y$$

solving for a ,

$$a = \frac{A_s f_y}{0.85f'_c b} = \frac{\rho f_y d}{0.85f'_c}$$

$$M_n = T \left(d - \frac{a}{2} \right) = A_s f_y \left(d - \frac{a}{2} \right)$$

$$M_u = \phi M_n$$

$$M_u = \phi M_n = \phi A_s f_y \left(d - \frac{a}{2} \right)$$

$$M_u = \phi A_s f_y d \left(1 - 0.59 \frac{\rho f_y}{f'_c} \right)$$

$$\epsilon_t = \frac{d - c}{c} (0.003)$$


$$\rho = \frac{A_s}{bd}$$

Balance Condition

From similar triangles at balance condition:

$$\frac{c}{d} = \frac{0.003}{0.003 + (f_y/E_s)} = \frac{0.003}{0.003 + (f_y/29 \times 10^6)}$$

$$c = \frac{87,000}{87,000 + f_y} d$$

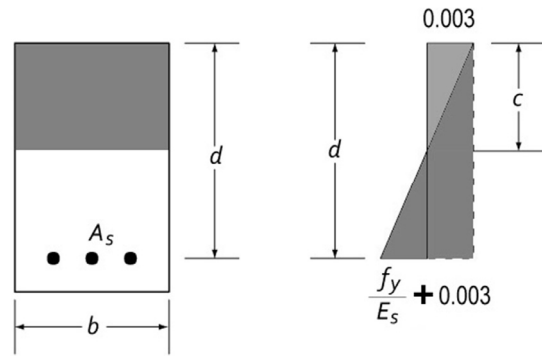

Use equation for a. Substitute into $c = a / \beta_1$

$$a = \frac{\rho f_y d}{0.85 f'_c} \quad \rho = \frac{A_s}{bd}$$

$$c = \frac{a}{\beta_1} = \frac{\rho f_y d}{0.85 \beta_1 f'_c}$$

Equate expressions for c:

$$\frac{\rho f_y d}{0.85 \beta_1 f'_c} = \frac{87,000}{87,000 + f_y} d$$

$$\rho_b = \left(\frac{0.85 \beta_1 f'_c}{f_y} \right) \left(\frac{87,000}{87,000 + f_y} \right)$$

Strain diagram for balanced condition.

Table A.8 Balanced Ratio of Reinforcement ρ_b for Rectangular Sections with Tension Reinforcement Only

f_y	f'_c	2,500 psi	3,000 psi	4,000 psi	5,000 psi	6,000 psi
		(17.2 MPa)	(20.7 MPa)	(27.6 MPa)	(34.5 MPa)	(41.4 MPa)
		$\beta_1 = 0.85$	$\beta_1 = 0.85$	$\beta_1 = 0.85$	$\beta_1 = 0.80$	$\beta_1 = 0.75$
Grade 40 40,000 psi (275.8 MPa)	ρ_b	0.0309	0.0371	0.0495	0.0582	0.0655
	$0.75 \rho_b$	0.0232	0.0278	0.0371	0.0437	0.0492
	$0.50 \rho_b$	0.0155	0.0186	0.0247	0.0291	0.0328
Grade 50 50,000 psi (344.8 MPa)	ρ_b	0.0229	0.0275	0.0367	0.0432	0.0486
	$0.75 \rho_b$	0.0172	0.0206	0.0275	0.0324	0.0365
	$0.50 \rho_b$	0.0115	0.0138	0.0184	0.0216	0.0243
Grade 60 60,000 psi (413.7 MPa)	ρ_b	0.0178	0.0214	0.0285	0.0335	0.0377
	$0.75 \rho_b$	0.0134	0.0161	0.0214	0.0252	0.0283
	$0.50 \rho_b$	0.0089	0.0107	0.0143	0.0168	0.0189
Grade 75 75,000 psi (517.1 MPa)	ρ_b	0.0129	0.0155	0.0207	0.0243	0.0274
	$0.75 \rho_b$	0.0097	0.0116	0.0155	0.0182	0.0205
	$0.50 \rho_b$	0.0065	0.0078	0.0104	0.0122	0.0137


Rectangular Beam Analysis

Data:

- Section dimensions – b, h, d, (span)
- Steel area - A_s
- Material properties – f'_c , f_y

Required:

- Nominal Strength (of beam) Moment - M_n
- Required (by load) Design Moment – M_u
- Load capacity

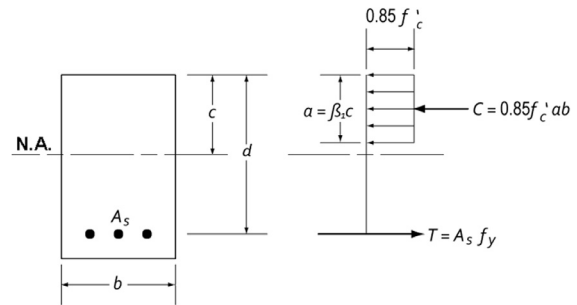

$A_{s,min}$
greater of a and b.

$$c = \frac{a}{\beta_1}$$

$$\epsilon_t = \frac{d-c}{c} 0.003 \geq 0.005$$

1. Calculate d
2. Check A_s min
3. Calculate a
4. Determine c

(a) $\frac{3\sqrt{f'_c}}{f_y} b_w d$

(b) $\frac{200}{f_y} b_w d$

$$a = \frac{A_s f_y}{0.85 f'_c b}$$

$$M_n = A_s f_y \left(d - \frac{a}{2} \right)$$

$$\phi M_n \geq M_u$$

5. Check that $\epsilon_t \geq 0.005$ (tension controlled)
6. Find nominal moment, M_n
7. Calculate required moment, $\phi M_n \geq M_u$
(if $\epsilon_t \geq 0.005$ then $\phi = 0.9$)
8. Determine max. loading (or span)

$$M_u = \frac{(1.2w_{DL} + 1.6w_{LL})l^2}{8}$$

$$1.6w_{LL} = \frac{M_u 8}{l^2} - 1.2w_{DL}$$



Rectangular Beam Analysis

Data:

- dimensions – 12"x23"
- Steel – 4 x # 6 $f_y = 60\text{ksi}$
- Concrete $f'_c = 6000\text{ psi}$
- Stirrup # 3 cover 1.5" Agg $\frac{3}{4}$ "

Required:

- Required Moment – $\phi M_n = M_u$ (capacity)

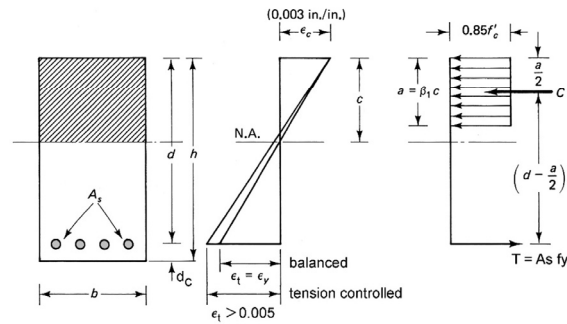


1. Calculate d

$$d_c = \text{COVER} + \#3 + \frac{1}{2}(\#6)$$

$$= 1.5 + 0.375 + \frac{0.75}{2} = 2.25"$$

$$d = h - d_c = 23" - 2.25 = 20.75"$$

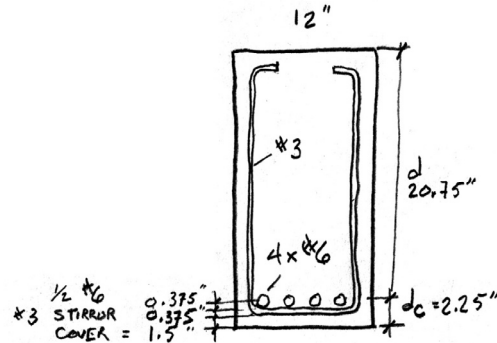

Rectangular Beam Analysis cont.

Data:

- dimensions – 12"x23"
- Steel – 4 x # 6 – $A_s = 1.76\text{ in}^2$
- $f'_c = 6000\text{ psi}$ $f_y = 60\text{ksi}$

Table A.2 Designations, Areas, Perimeters, and Weights of Standard Bars

Bar No.	Customary Units			SI Units		
	Diameter (in.)	Cross-sectional Area (in. ²)	Unit Weight (lb/ft)	Diameter (mm)	Cross-sectional Area (mm ²)	Unit Weight (kg/m)
3	0.375	0.11	0.376	9.52	71	0.560
4	0.500	0.20	0.668	12.70	129	0.994
5	0.625	0.31	1.043	15.88	200	1.552
6	0.750	0.44	1.502	19.05	284	2.235
7	0.875	0.60	2.044	22.22	387	3.042
8	1.000	0.79	2.670	25.40	510	3.973
9	1.128	1.00	3.400	28.65	645	5.060
10	1.270	1.27	4.303	32.26	819	6.404
11	1.410	1.56	5.313	35.81	1006	7.907
14	1.693	2.25	7.650	43.00	1452	11.384
18	2.257	4.00	13.600	57.33	2581	20.238

2. Check A_s, min

$A_s \text{ min}$

$$\textcircled{1} \frac{3\sqrt{f'_c}}{f_y} b d = \frac{3\sqrt{6000}}{60000} (12 \times 20.75) = 0.964\text{ in}^2 \leftarrow \text{controls}$$

$$\textcircled{2} \frac{200 b d}{f_y} = \frac{200 (12) (20.75)}{60000} = 0.83\text{ in}^2$$

$$\therefore A_s \text{ min} = 0.964\text{ in}^2$$

$$A_s = A_b \text{ (N.B.)} = 0.44 (4) = 1.76\text{ in}^2 \checkmark > 0.964\text{ in}^2$$

Rectangular Beam Analysis cont.


Data:

dimensions – 12"x23"

Steel – 4 x # 6 – $A_s = 1.76 \text{ in}^2$

$f'_c = 6000 \text{ psi}$ $f_y = 60 \text{ ksi}$

f'_c	β_1
0	0.85
1000	0.85
2000	0.85
3000	0.85
4000	0.85
5000	0.8
6000	0.75
7000	0.7
8000	0.65
9000	0.65
10000	0.65

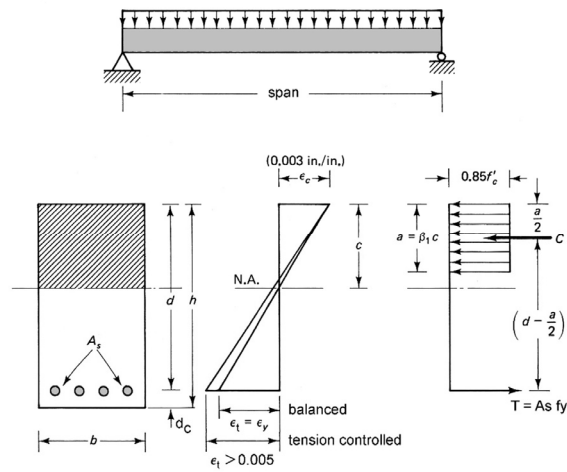

3. Find a

$$a = \frac{A_s f_y}{0.85 f'_c b} = \frac{(1.76)(60)}{0.85(6)(12)} = 1.725''$$

4. Find c

$$\beta_1 = 0.85 - 0.05 \frac{f'_c - 4000}{1000} = 0.85 - 0.1 = 0.75$$

$$c = \frac{a}{\beta_1} = \frac{1.725}{0.75} = 2.300''$$

Rectangular Beam Analysis cont.


5. Check that A_s is $< A_s \text{ max}$

$$\epsilon_t \geq 0.004$$

6. Check that $\epsilon_t \geq 0.005$

(for tension controlled section)

$$\phi = 0.9$$

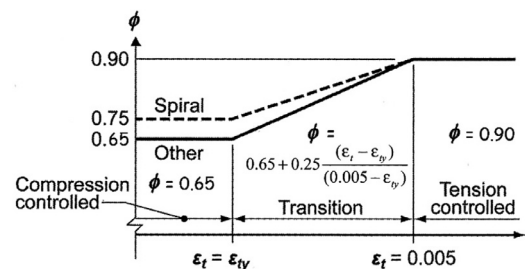

$$\epsilon_t = \frac{d-c}{c} 0.003 = \frac{20.75-2.3}{2.3} 0.003$$

$$= 0.02406 > 0.004 \quad \therefore \text{OK} \checkmark$$

$$= 0.02406 > 0.005 \quad \therefore \text{tension controlled}$$

7. Find nominal moment, M_n

$$T = A_s f_y = 1.76 (60 \text{ ksi}) = 105.6 \text{ K}$$

$$M_n = T \left(d - \frac{a}{2} \right) = 105.6 \left(20.75 - \frac{1.725}{2} \right)$$

$$M_n = 2100 \text{ K-in}$$

8. Calculate required moment

$$\phi M_n \geq M_u$$

$$\phi M_n = 0.9 (2100) = 1890 \text{ K-in}$$

$$M_u = \phi M_n = 1890 / 12 = \underline{157.5 \text{ K-ft}}$$



Slab Analysis

Data:

- Span = 18 ft
- $h = 11''$
take $b = 12''$
- Steel #8 @ 18" o.c.
- $f_c = 3000$ psi
- $f_y = 60$ ksi

Required:

- Design moment capacity – M_u
- Maximum LL in PSF

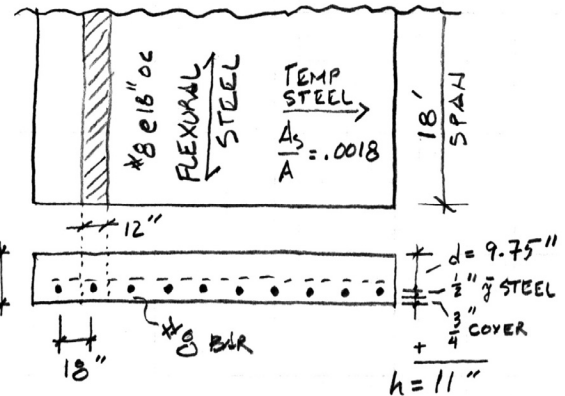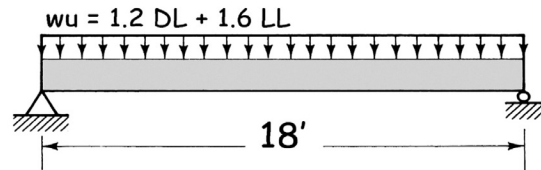

$$d = 11'' - \frac{1}{2}'' - \frac{3}{4}'' = 9.75''$$

$$A_s = \frac{12''}{18''} (0.79 \text{ in}^2) = 0.5267 \text{ in}^2/\text{FT}$$

1. Find d
2. Find A_s
Check $A_{s,min}$

$$A_g = 11'' \times 12'' = 132 \text{ in}^2$$

$$[0.0018(60)/60] 132 = 0.237 \text{ in}^2$$

$$0.0014 (132) = 0.1848 \text{ in}^2$$

$$0.527 > 0.237 \text{ ok}$$

Table 7.6.1.1— $A_{s,min}$ for nonprestressed one-way slabs

Reinforcement type	f_y , psi	$A_{s,min}$
Deformed bars	< 60,000	$0.0020A_g$
Deformed bars or welded wire reinforcement	$\geq 60,000$	Greater of: $\frac{0.0018 \times 60,000}{f_y} A_g$
		$0.0014A_g$


ACI 318-14

Slab Analysis

f_c	β_1
0	0.85
1000	0.85
2000	0.85
3000	0.85
4000	0.85
5000	0.8
6000	0.75
7000	0.7
8000	0.65
9000	0.65
10000	0.65

3. Find a

$$d = \frac{A_s f_y}{.85 f_c' b} = \frac{0.5267 (60)}{.85 (3) (12)} = 1.033''$$

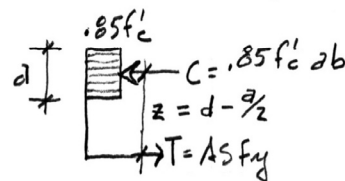

4. Find $c = \beta_1 a$

$$c = \frac{a}{\beta_1} = \frac{1.033''}{0.85} = 1.215''$$

5. Check failure mode

$$\epsilon_t \geq 0.005 \text{ for tension controlled}$$

$$\epsilon_t = \frac{0.003 d}{c} - 0.003$$

$$\epsilon_t = \frac{0.003 (9.75'')}{1.215''} - 0.003 = 0.021 \%$$

6. Find force T

$$\epsilon_t = 0.021 > 0.005 \therefore \text{TENSION CONTROLLED}$$

7. Find moment arm z


$$T = A_s f_y = 0.5267 (60) = 31.6 \text{ K}$$

$$z = d - \frac{a}{2} = 9.75 - \frac{1.033}{2} = 9.23''$$

8. Find nominal strength moment, M_n

$$M_n = T z = 31.6 (9.23) = 291.8 \text{ K-in}$$

Slab Analysis

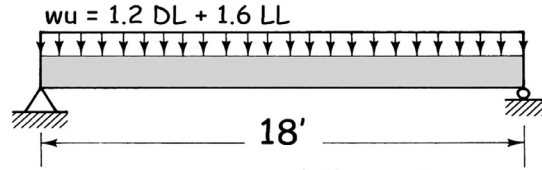

9. Find required moment, M_u

$$M_u = \phi M_n = 0.9 (291.8) \frac{1000}{12} = 21885 \text{ l-ft}$$

10. Find slab DL

$$w_{DL} = 2 \frac{h}{12} = 150 \frac{11}{12} = 137.5 \text{ PSF}$$

11. Determine max. loading

$$M_u = 21885 \text{ l-ft} = \frac{(1.2 w_{DL} + 1.6 w_{LL}) l^2}{8}$$

$$\frac{21885 (8)}{(18')^2} = 1.2 (137.5) + 1.6 (w_{LL})$$

$$540.37 = 165 + 1.6 (w_{LL})$$

$$w_{LL} = 234.6 \text{ PSF}$$

Details of Reinforcement


Size

- Nominal 1/8" increments

Grade

- 40 40 ksi
- 60 60 ksi
- 75 75 ksi

Bar size designation	Nominal cross section area, sq. in.	Weight, lb per ft	Nominal diameter, in.
#3	0.11	0.376	0.375
#4	0.20	0.668	0.500
#5	0.31	1.043	0.625
#6	0.44	1.502	0.750
#7	0.60	2.044	0.875
#8	0.79	2.670	1.000
#9	1.00	3.400	1.128
#10	1.27	4.303	1.270
#11	1.56	5.313	1.410
#14	2.25	7.650	1.693
#18	4.00	13.600	2.257

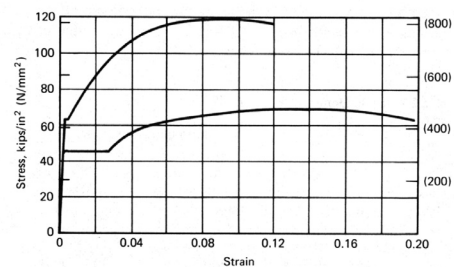


Details of Reinforcement

ACI 318 Chapter 25.2 Placement of Reinforcement

- cover (ACI 20.6.1)
- horizontal spacing in beams (ACI 25.2.1)
1 inch
 d_b
 $4/3$ max aggregate
- vertical spacing in beams (ACI 25.2.2)
1 inch

Table 20.6.1.3.1—Specified concrete cover for cast-in-place nonprestressed concrete members


Concrete exposure	Member	Reinforcement	Specified cover, in.
Cast against and permanently in contact with ground	All	All	3
Exposed to weather or in contact with ground	All	No. 6 through No. 18 bars	2
		No. 5 bar, W31 or D31 wire, and smaller	1-1/2
Not exposed to weather or in contact with ground	Slabs, joists, and walls	No. 14 and No. 18 bars	1-1/2
		No. 11 bar and smaller	3/4
	Beams, columns, pedestals, and tension ties	Primary reinforcement, stirrups, ties, spirals, and hoops	1-1/2

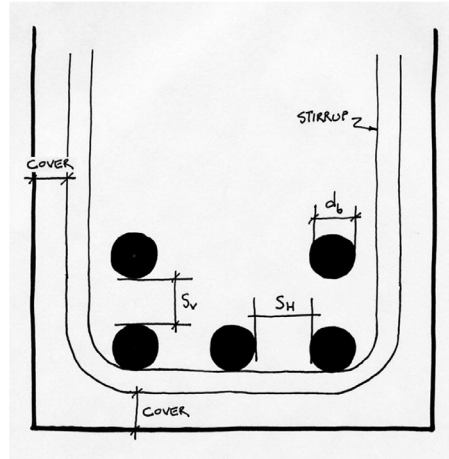

Details of Reinforcement

ACI 318 Chapter 25 Placement of Reinforcement

- Chairs
- Bolsters

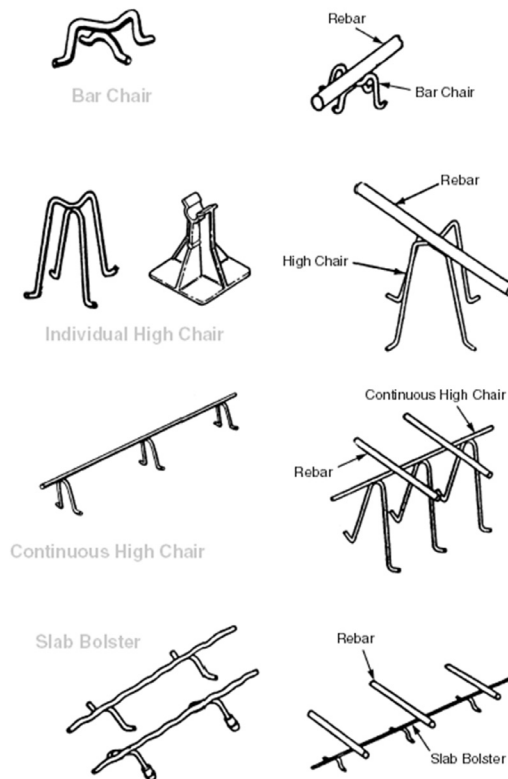

Details of Reinforcement

ACI 318 Chapter 25

Minimum bend diameter

- factor x d_b

Hooks for bars in tension

- ACI Table 25.3.1
- Inside diameter

Bends for stirrups

- ACI Table 25.3.2

Table 25.3.1—Standard hook geometry for development of deformed bars in tension

Type of standard hook	Bar size	Minimum inside bend diameter, in.	Straight extension ⁽¹⁾ ℓ_{ext} , in.	Type of standard hook
90-degree hook	No. 3 through No. 8	$6d_b$	$12d_b$	
	No. 9 through No. 11	$8d_b$		
	No. 14 and No. 18	$10d_b$		
180-degree hook	No. 3 through No. 8	$6d_b$	Greater of $4d_b$ and 2.5 in.	
	No. 9 through No. 11	$8d_b$		
	No. 14 and No. 18	$10d_b$		

⁽¹⁾A standard hook for deformed bars in tension includes the specific inside bend diameter and straight extension length. It shall be permitted to use a longer straight extension at the end of a hook. A longer extension shall not be considered to increase the anchorage capacity of the hook.

Table 25.3.2—Minimum inside bend diameters and standard hook geometry for stirrups, ties, and hoops

Type of standard hook	Bar size	Minimum inside bend diameter, in.	Straight extension ⁽¹⁾ ℓ_{ext} , in.	Type of standard hook
90-degree hook	No. 3 through No. 5	$4d_b$	Greater of $6d_b$ and 3 in.	
	No. 6 through No. 8	$6d_b$	$12d_b$	
135-degree hook	No. 3 through No. 5	$4d_b$	Greater of $6d_b$ and 3 in.	
	No. 6 through No. 8	$6d_b$		
180-degree hook	No. 3 through No. 5	$4d_b$	Greater of $4d_b$ and 2.5 in.	
	No. 6 through No. 8	$6d_b$		

⁽¹⁾A standard hook for stirrups, ties, and hoops includes the specific inside bend diameter and straight extension length. It shall be permitted to use a longer straight extension at the end of a hook. A longer extension shall not be considered to increase the anchorage capacity of the hook.

Details of Reinforcement

ACI 318 Chapter 25

Development length of bars

- 12" minimum
- based on table 25.4.2.2

Table 25.4.2.4—Modification factors for development of deformed bars and deformed wires in tension

Modification factor	Condition	Value of factor
Lightweight λ	Lightweight concrete	0.75
	Lightweight concrete, where f_{cr} is specified	In accordance with 19.2.4.3
	Normalweight concrete	1.0
Epoxy ⁽¹⁾ ψ_e	Epoxy-coated or zinc and epoxy dual-coated reinforcement with clear cover less than $3d_b$ or clear spacing less than $6d_b$	1.5
	Epoxy-coated or zinc and epoxy dual-coated reinforcement for all other conditions	1.2
	Uncoated or zinc-coated (galvanized) reinforcement	1.0
Size ψ_s	No. 7 and larger bars	1.0
	No. 6 and smaller bars and deformed wires	0.8
Casting position ⁽¹⁾ ψ_t	More than 12 in. of fresh concrete placed below horizontal reinforcement	1.3
	Other	1.0

⁽¹⁾The product $\psi_s\psi_t$ need not exceed 1.7.

Table 25.4.2.2—Development length for deformed bars and deformed wires in tension

Spacing and cover	No. 6 and smaller bars and deformed wires	No. 7 and larger bars
Clear spacing of bars or wires being developed or lap spliced not less than d_b , clear cover at least d_b , and stirrups or ties throughout ℓ_d not less than the Code minimum or Clear spacing of bars or wires being developed or lap spliced at least $2d_b$ and clear cover at least d_b	$\left(\frac{f_y \psi_s \psi_e}{25 \lambda \sqrt{f'_c}} \right) d_b$	$\left(\frac{f_y \psi_s \psi_e}{20 \lambda \sqrt{f'_c}} \right) d_b$
Other cases	$\left(\frac{3 f_y \psi_s \psi_e}{50 \lambda \sqrt{f'_c}} \right) d_b$	$\left(\frac{3 f_y \psi_s \psi_e}{40 \lambda \sqrt{f'_c}} \right) d_b$

Other Useful Tables:

Table A.1 Values of Modulus of Elasticity for Normal-Weight Concrete

Customary Units		SI Units	
f'_c (psi)	E_c (psi)	f'_c (MPa)	E_c (MPa)
3,000	3,140,000	20.7	21 650
3,500	3,390,000	24.1	23 373
4,000	3,620,000	27.6	24 959
4,500	3,850,000	31.0	26 545
5,000	4,050,000	34.5	27 924

Jack C McCormac, 1978
Design of Reinforced Concrete,

Table A.2 Designations, Areas, Perimeters, and Weights of Standard Bars

Bar No.	Customary Units			SI Units		
	Diameter (in.)	Cross-sectional Area (in. ²)	Unit Weight (lb/ft)	Diameter (mm)	Cross-sectional Area (mm ²)	Unit Weight (kg/m)
3	0.375	0.11	0.376	9.52	71	0.560
4	0.500	0.20	0.668	12.70	129	0.994
5	0.625	0.31	1.043	15.88	200	1.552
6	0.750	0.44	1.502	19.05	284	2.235
7	0.875	0.60	2.044	22.22	387	3.042
8	1.000	0.79	2.670	25.40	510	3.973
9	1.128	1.00	3.400	28.65	645	5.060
10	1.270	1.27	4.303	32.26	819	6.404
11	1.410	1.56	5.313	35.81	1006	7.907
14	1.693	2.25	7.650	43.00	1452	11.384
18	2.257	4.00	13.600	57.33	2581	20.238

Table A.4 Areas of Groups of Standard Bars (in.²)

Bar No.	Number of Bars													
	2	3	4	5	6	7	8	9	10	11	12	13	14	
4	0.39	0.58	0.78	0.98	1.18	1.37	1.57	1.77	1.96	2.16	2.36	2.55	2.75	
5	0.61	0.91	1.23	1.53	1.84	2.15	2.45	2.76	3.07	3.37	3.68	3.99	4.30	
6	0.88	1.32	1.77	2.21	2.65	3.09	3.53	3.98	4.42	4.86	5.30	5.74	6.19	
7	1.20	1.80	2.41	3.01	3.61	4.21	4.81	5.41	6.01	6.61	7.22	7.82	8.42	
8	1.57	2.35	3.14	3.93	4.71	5.50	6.28	7.07	7.85	8.64	9.43	10.21	11.00	
9	2.00	3.00	4.00	5.00	6.00	7.00	8.00	9.00	10.00	11.00	12.00	13.00	14.00	
10	2.53	3.79	5.06	6.33	7.59	8.86	10.12	11.39	12.66	13.92	15.19	16.45	17.72	
11	3.12	4.68	6.25	7.81	9.37	10.94	12.50	14.06	15.62	17.19	18.75	20.31	21.87	
14	4.50	6.75	9.00	11.25	13.50	15.75	18.00	20.25	22.50	24.75	27.00	29.25	31.50	
18	8.00	12.00	16.00	20.00	24.00	28.00	32.00	36.00	40.00	44.00	48.00	52.00	56.00	

Rectangular Beam Design

Two approaches:


Method 1:

Data:

- Load and Span
- Material properties – f'_c , f_y
- All section dimensions: h and b

Required:

- Steel area - A_s

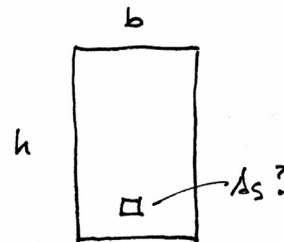


Method 2:

Data:

- Load and Span
- Some section dimensions – h or b
- Material properties – f'_c , f_y
- ρ

Required:

- Steel area - A_s
- Beam dimensions – b and h

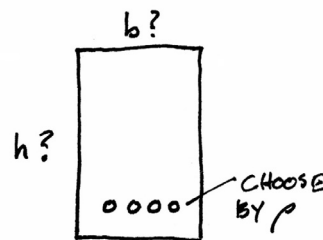


Rectangular Beam Design – method 1

Data:

- Load and Span
- Material properties – f'_c , f_y
- All section dimensions – b and h

Required:

- Steel area - A_s

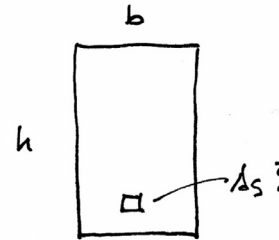

1. Calculate the factored load and find factored required moment, M_u
2. Find $d = h - \text{cover} - \text{stirrup} - d_b/2$ (one layer)
3. Estimate moment arm $z = jd$. For beams $j \approx 0.9$ for slabs $j \approx 0.95$
4. Estimate A_s based on estimate of jd .
5. Use A_s to find a
6. Use a to find A_s (repeat...until 2% accuracy)
7. Choose bars for A_s and check A_s max & min
8. Check that $\epsilon_t \geq 0.005$
9. Check $M_u \leq \phi M_n$ (final condition)

$$M_u = \frac{(\gamma w_{DL} + \gamma w_{LL})l^2}{8}$$

$$A_s = \frac{M_u}{\phi f_y \left(d - \frac{a}{2} \right)}$$

$$a = \frac{A_s f_y}{0.85 f'_c b}$$


10. Design shear reinforcement (stirrups)
11. Check deflection, crack control, steel development length.

$$M_n = A_s f_y \left(d - \frac{a}{2} \right)$$

Rectangular Slab Design

Data:

- Load and Span
- Material properties – f'_c , f_y
- All section dimensions:
- h (based on deflection limit)
- $b = \text{typical } 12'' \text{ width}$

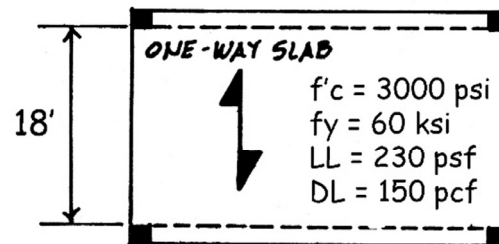

Required:

- Steel area - A_s

First estimate the slab thickness, h .

Try first the recommended minimum.

Deeper sections require less steel, but of course more concrete.


Table 7.3.1—Minimum thickness of solid nonprestressed one-way slabs

Support condition	Minimum $h^{(1)}$
Simply supported	$l/20$
One end continuous	$l/24$
Both ends continuous	$l/28$
Cantilever	$l/10$

THICKNESS, h , BASED ON DEFLECTION

$$h = \frac{l}{20} = \frac{18 \times 12}{20} = 10.8'' \text{ USE } 11''$$

Rectangular Slab Design

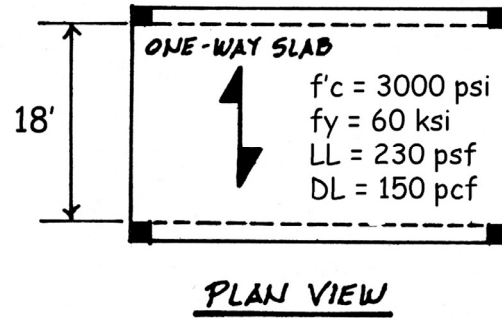

1. Calculate the dead load and find required M_u

FACTOR LOADS

$$DL = \frac{11''}{12} (150) = 137.5 \text{ PSF}$$


$$LL \text{ (GIVEN)} = 230 \text{ PSF}$$

$$w_u = 1.2(137.5) + 1.6(230) = 533$$

$$M_u = \frac{w_u l^2}{8} = \frac{533 \text{ PLF} (18')^2}{8} = 21587 \text{ '}\cdot\text{K}$$

$$= 259 \text{ '}\cdot\text{K}$$

Rectangular Slab Design

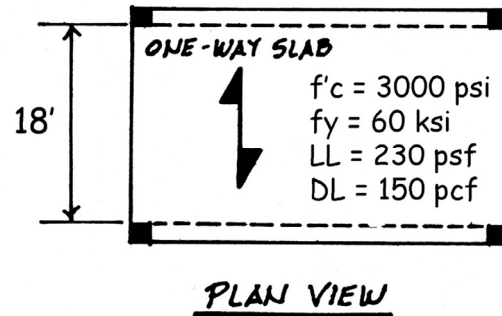

2. Estimate moment arm
 $z \approx 0.95 d$

FOR $j \approx 0.95$, $d = h - \text{COVER} - \frac{1}{2} \text{ BAR}$

$$d = 11'' - \frac{3}{4}'' - \frac{1}{2} (\frac{1}{2}'')$$

$$d = 11'' - 1'' = 10''$$

$$z \approx j d \approx 0.95 (10'') = 9.5''$$

Rectangular Slab Design

3. Estimate A_s based on estimate of j_d .
4. Use A_s to find a
5. Use a to find A_s (repeat...)

TRIAL 1

$$A_s = \frac{M_u}{\phi f_y (z)} = \frac{259 \text{ in}^{\text{-k}}}{0.9(60 \text{ ksi})(9.5 \text{ in})} = 0.505 \text{ in}^2$$

$$a = \frac{A_s f_y}{.85 f'_c b} = \frac{0.505(60)}{.85(3)(12)} = 0.99 \text{ in}$$

TRIAL 2

$$A_s = \frac{M_u}{\phi f_y (d - \frac{a}{2})} = \frac{259}{0.9(60)(10 - \frac{.99}{2})}$$

$$A_s = 0.5046 \text{ in}^2 \quad \text{WITHIN 2\%}$$

Rectangular Slab Design

6. Choose bars for A_s required:
 - either
 - choose bars** and calculate spacing
 - or
 - choose spacing** and find bar size

If the bar size changes, re-calculate to find new d . Then re-calculate A_s ...

7. Check $A_{s,min}$ (for slabs $A_{s,min}$ from ACI Table 7.6.1.1)

Table 7.6.1.1— $A_{s,min}$ for nonprestressed one-way slabs

Reinforcement type	f_y , psi		$A_{s,min}$
Deformed bars	< 60,000		$0.0020A_g$
Deformed bars or welded wire reinforcement	$\geq 60,000$	Greater of:	$\frac{0.0018 \times 60,000}{f_y} A_g$
			$0.0014A_g$

CHOOSE BARS

USING #4

$$\frac{0.505}{12 \text{ in}} ; \frac{0.2}{s} \quad s = 4.75 \text{ in}$$

\therefore USE #4 @ 4" o.c. (always round down)

$$A_s = 0.60 \text{ in}^2/\text{FT} > 0.505 \checkmark$$

ALTERNATE FOR MAX. S = 18"

$$\frac{0.505}{12 \text{ in}} ; \frac{A_b}{18 \text{ in}} \quad A_b = 0.75 \text{ in}^2$$

$$\#8 = 0.79$$

\therefore USE #8 @ 18" o.c.

$$A_s = 0.526 \text{ in}^2/\text{FT} > 0.505 \checkmark$$

Check $A_{s,min}$

$$A_{s,min} = 0.0018 bh = 0.0018(12)(11 \text{ in})$$

$$= 0.24 \text{ in}^2 < 0.526 \text{ in}^2 \checkmark \text{ OK}$$

Rectangular Slab Design

8. Check that $\epsilon_t \geq 0.005$

$$\text{RE-CALC 2 FOR } A_s = 0.6 \text{ m}^2/\text{ft}$$
$$a = \frac{A_s f_y}{0.85 F'_c b} = \frac{0.6(60)}{0.85(3)(12)} = 1.176''$$

$$c = \frac{a}{\beta_1} = \frac{1.176}{0.85} = 1.384''$$

$$\epsilon_t = \frac{d-c}{c} 0.003 =$$
$$= \frac{9.5'' - 1.384''}{1.384''} 0.003 = 0.01759$$

$$0.01759 > 0.005$$

\therefore TENSION CONTROLLED \checkmark

Rectangular Slab Design

9. Check $M_u \leq \phi M_n$
(final condition)
 $A_s = A_{s, \text{used}}$

$$M_n = T z$$

$$M_n = A_s f_y \left(d - \frac{a}{2} \right)$$

$$M_n = 0.6(60) \left(9.5'' - \frac{1.176}{2} \right)$$

$$M_n = 36(8.911'') = 320.8 \text{ k-in}$$

$$\phi M_n = 0.9(320.8) = 288.7 \text{ k-in}$$

10. Check deflection, crack control, steel development length.

$$M_u = 259 \text{ k-in} < 288.7 \text{ k-in}$$

$$M_u < \phi M_n \checkmark \text{ OK}$$

Rectangular Beam Design – method 2

Data:

- Load and Span
- Some section dimensions – b or h
- Material properties – f'_c , f_y

$$M_u = \frac{(\gamma w_{DL} + \gamma w_{LL})l^2}{8}$$

Required:

- Steel area - A_s
 - Beam dimensions – b and h
1. Estimate the dead load ($h \approx L/12$) and find M_u
 2. Choose ρ (equation assumes $\epsilon_t = 0.0075$)
 3. Calculate bd^2
 4. Choose b and solve for d (or d and solve b)
b is based on form size – matches column size
h is between $L/12$ to $L/18$ and $b:h \approx 1:2$ to $2:3$
 5. Estimate h and correct weight and M_u
 6. Find $A_s = \rho b d$
 7. Choose bars for A_s and determine spacing and cover. Recheck h and weight.
 8. Check that $\epsilon_t \geq 0.005$ (if not, increase h and reduce A_s)
 9. Design shear reinforcement (stirrups)
 10. Check deflection, crack control, steel development length.

$$\rho = \frac{\beta_1 f'_c}{4 f_y}$$

$$b d^2 = \frac{M_u}{\phi \rho f_y (1 - 0.59 \rho (f_y / f'_c))}$$

$$A_s = \rho b d$$

$$a = \frac{\rho f_y d}{0.85 f'_c}$$

Rectangular Beam Design

Data:

- Load and Span
- Material properties – f'_c , f_y

Required:

- Steel area - A_s
- Beam dimensions – b and d

Estimate b and h to get beam selfweight.

1. Estimate the dead load ($h \approx L/12$) and find M_u .

Table 9.3.1.1—Minimum depth of nonprestressed beams


Support condition	Minimum $h^{(1)}$
Simply supported	$l/16$
One end continuous	$l/18.5$
Both ends continuous	$l/21$
Cantilever	$l/8$

⁽¹⁾Expressions applicable for normalweight concrete and $f_y = 60,000$ psi. For other cases, minimum h shall be modified in accordance with 9.3.1.1.1 through 9.3.1.1.3, as appropriate.

2. Choose ρ (equation assumes $\epsilon_t = 0.0075$)

$f'_c = 3000$ psi
 $f_y = 60$ ksi

DL = 2 klf + beam
LL = 2 x 20 k

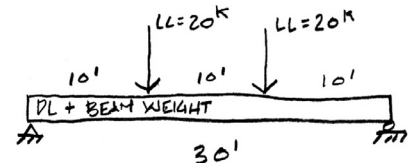

$$\text{ASSUME } h \approx \frac{L}{12} = \frac{360''}{12} = 30''$$

$$\text{ASSUME } b:h \approx 1:2 \therefore b \approx 15''$$

$$\text{BEAM DL} = 150 \frac{15 \times 30}{144} = 469 \text{ PLF}$$

ESTIMATE M_u

$$\begin{aligned} M_u &= P_o + \frac{w l^2}{8} \\ &= 1.6(20)(10') + \frac{1.2(2.469 \text{ KLF})(30')^2}{8} \\ &= 320 + 333.3 = 653.3 \text{ K-}' \end{aligned}$$

CHOOSE ρ

$$\rho = \frac{\beta_1 f'_c}{4 f_y} = \frac{0.85(3)}{4(60)} = 0.010$$

Rectangular Beam Design cont.

3. Calculate bd^2

$$bd^2 = \frac{M_u}{\phi \rho F_y (1 - 0.59 \rho (f_y / f_c))}$$

$$bd^2 = \frac{653.3 (12)}{0.01(0.9)60 [1 - 0.59(0.01)(\frac{60}{3})]}$$

$$bd^2 = \frac{7840}{0.573(0.882)} = 15492 \text{ in}^3$$

4. Choose b and solve for d

(or d and solve for b)

b is based on form size – matches column size

h is between $L/12$ to $L/18$ and $b:h \approx 1:2$ to $2:3$

TRY

b	d	$h \approx 1.12 d$	A
14"	33.27"	38"	532
15"	32.14"	36"	540
16"	31.11"	35"	560

5. Estimate h and correct weight and M_u

CHOOSE 15 x 36

Rectangular Beam Design cont.

6. Choose b and solve for d

(or d and solve for b)

b is based on form size – matches column size

h is between $L/12$ to $L/18$ and $b:h \approx 1:2$ to $2:3$

USE 15 x 36

$$\text{REVISE } PL = 150 \frac{540}{144} = 563 \text{ PLF}$$

CHECK M_u

$$M_u = 320 + \frac{1.2(2,563)30^2}{8} = 666 \text{ K-ft}$$

REVISE bd

$$bd^2 = \frac{666(12)}{0.505} = 15814 \text{ in}^3$$

$$\text{FOR } b = 15" \quad d = 32.5"$$


8. Find $A_s = \rho bd$

$$A_s = \rho bd = (0.01)(15")(32.5")$$

$$A_s = 4.87 \text{ in}^2$$

Rectangular Beam Design


9. Choose bars for A_s and determine spacing and cover. Recheck h and weight.

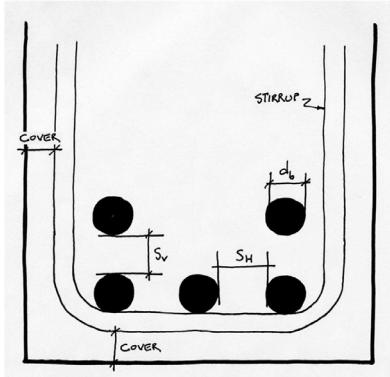

If bars do not fit in one layer, d is measured to the centroid of the pattern.

CHOOSE BARS (SEE TABLE A.4)

TRY 5 x #9 BARS $A_s = 5.0 \text{ in}^2$

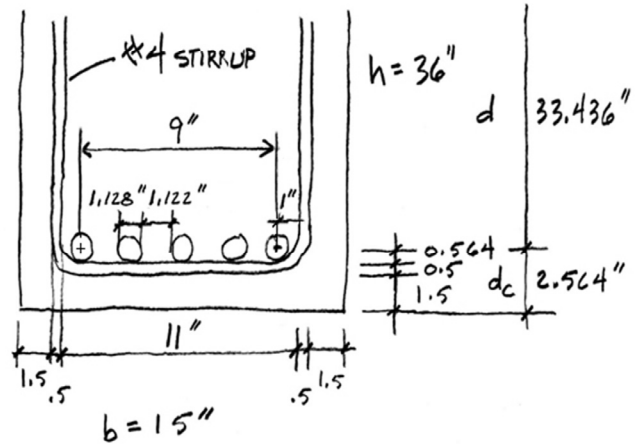

$$\bar{x} = \frac{\sum A \times d_x}{\sum A}$$

Table A.4 Areas of Groups of Standard Bars (in.²)

Bar No.	Number of Bars													
	2	3	4	5	6	7	8	9	10	11	12	13	14	
4	0.39	0.58	0.78	0.98	1.18	1.37	1.57	1.77	1.96	2.16	2.36	2.55	2.75	
5	0.61	0.91	1.23	1.53	1.84	2.15	2.45	2.76	3.07	3.37	3.68	3.99	4.30	
6	0.88	1.32	1.77	2.21	2.65	3.09	3.53	3.98	4.42	4.86	5.30	5.74	6.19	
7	1.20	1.80	2.41	3.01	3.61	4.21	4.81	5.41	6.01	6.61	7.22	7.82	8.42	
8	1.57	2.35	3.14	3.93	4.71	5.50	6.28	7.07	7.85	8.64	9.43	10.21	11.00	
9	2.00	3.00	4.00	5.00	6.00	7.00	8.00	9.00	10.00	11.00	12.00	13.00	14.00	
10	2.53	3.79	5.06	6.33	7.59	8.86	10.12	11.39	12.66	13.92	15.19	16.45	17.72	
11	3.12	4.68	6.25	7.81	9.37	10.94	12.50	14.06	15.62	17.19	18.75	20.31	21.87	
14	4.50	6.75	9.00	11.25	13.50	15.75	18.00	20.25	22.50	24.75	27.00	29.25	31.50	
18	8.00	12.00	16.00	20.00	24.00	28.00	32.00	36.00	40.00	44.00	48.00	52.00	56.00	

Jack C McCormac, 1978
Design of Reinforced Concrete,

Rectangular Beam Design

7. Choose bars for A_s and determine spacing and cover. Recheck h and weight.

$$d = 33.436''$$

$$a = \frac{A_s f_y}{0.85 f'_c b} = \frac{5(60)}{0.85(3)15} = 7.843''$$

Make final check of M_n using final d and Check that $M_u \leq \phi M_n$

$$M_n = A_s f_y \left(d - \frac{a}{2} \right) = 5(60) \left(33.436 - \frac{7.843}{2} \right)$$

$$M_n = 8854 \text{ K-in} = 737.8 \text{ K-ft}$$

$$\phi M_n = 0.9(737.8) = 664 \text{ K-ft}$$

$$M_u = 653.3 < 664 \quad \checkmark \text{ OK}$$

8. Check that $\epsilon_t \geq 0.005$ (if not, increase h and reduce A_s)

$$c = \frac{a}{\beta_1} = \frac{7.843}{0.85} = 9.227''$$

$$\epsilon_t = \frac{d-c}{c} (0.003)$$

9. Design shear reinforcement (stirrups)
10. Check deflection, crack control, steel development length.

$$\epsilon_t = \frac{33.436 - 9.227}{9.227} (0.003)$$

$$\epsilon_t = 0.00787 > 0.005 \quad \checkmark \text{ OK}$$


Non-Rectangular Beam Analysis

Data:

- Section dimensions – b , b_e , h , (span)
- Steel area - A_s
- Material properties – f'_c , f_y

Required:

- Required Moment – M_u (or load, or span)
1. Find $T = A_s f_y$ and $C = 0.85 f'_c A_c$
 2. Set $T = C$ and solve for A_c
 3. Draw and label diagrams for section and stress
 1. Determine b effective (for T-beams)
 2. Locate T and C (or C_1 and C_2)
 4. Determine the location of a .
Working from the top down,
add up area to make A_c
 5. Find moment arms (z) for each block of area
 6. Find $M_n = \sum C z$
 7. Find $M_u = \phi M_n$
 8. Check $A_{s \min} < A_s < A_{s \max}$
 9. Check that $\epsilon_t \geq 0.005$

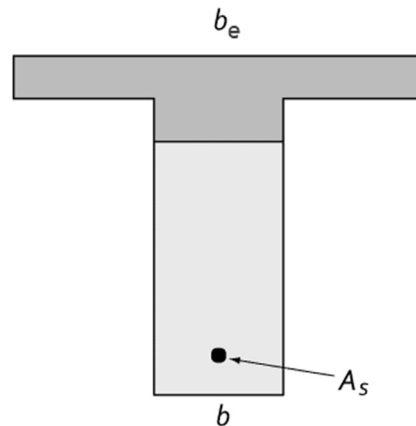


Effective Flange Width, b_e

Slab on one side:

b_e least of either (total width) or (overhang + stem)


- Total width: 1/12 of the beam span
- Overhang: 6 x slab thickness
- Overhang: 1/2 the clear distance to next beam

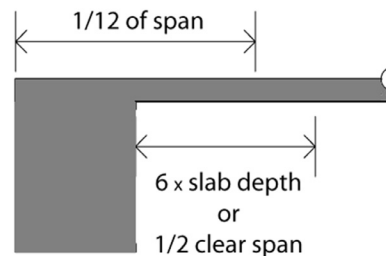

Slab on both sides:


b_e least of either (total width) or (2 x overhang + stem)

- Total width: 1/4 of the beam span
- Overhang: 8 x slab thickness
- Overhang: 1/2 the clear distance to next beam (i.e. the web on center spacing)

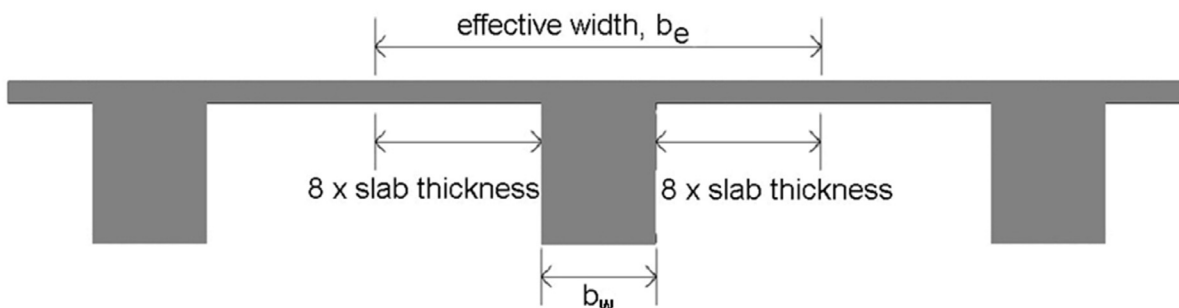

Non-rectangular shape - example

Given: $f'_c = 3000$ psi
 $f_y = 60$ ksi
 $A_s = 6 \times \#9 = 6 \text{ in}^2$
 Req'd: Capacity, M_u

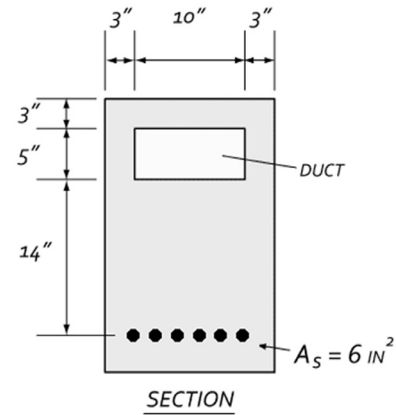

- 1a. Find T
- 1b. Find C in terms of A_c
2. Set $T = C$ and solve for A_c

$$T = A_s f_y = 6 \text{ in}^2 (60,000 \text{ psi})$$

$$T = 360,000 \text{ lb} = 360 \text{ k}$$

$$C = 0.85 f'_c A_c = 0.85 (3000 \text{ psi}) A_c \text{ in}^2$$

$$C = (2550 A_c) \text{ lb} = (2.55 A_c) \text{ k}$$

$$T = C$$


$$360 \text{ k} = 2.55 A_c \text{ k}$$

$$A_c = 142 \text{ in}^2$$

Non-rectangular shape (cont.)

3. Draw section and determine areas to make A_c
4. Find the location of a .
 $a = 3'' + 5'' + 4''$

$$C = 0.85 f'_c A_c$$

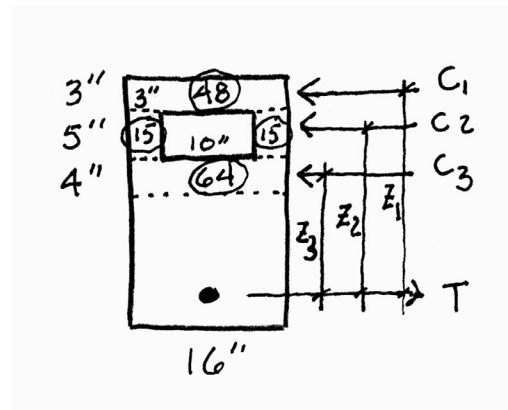

$f'_c = 3$ ksi
 $A_{c1} = 48 \text{ in}^2$
 $A_{c2} = 30 \text{ in}^2$
 $A_{c3} = 64 \text{ in}^2$

$$A_c = 142 \text{ in}^2 = A_{c1} + A_{c2} + A_{c3}$$

$$142 = 48 + 30 + A_{c3}$$

$$A_{c3} = 64 \text{ in}^2$$




$$C_1 = 48 (2.55) = 122.4 \text{ k}$$

$$C_2 = 30 (2.55) = 76.5 \text{ k}$$

$$C_3 = 64 (2.55) = 163.2 \text{ k}$$

Ferrocement

- Pioneered by Pier Luigi Nervi
- Dense, small gage reinforcement
- More flexible shapes – no formwork
- Well suited for thin shells
- Less cracking

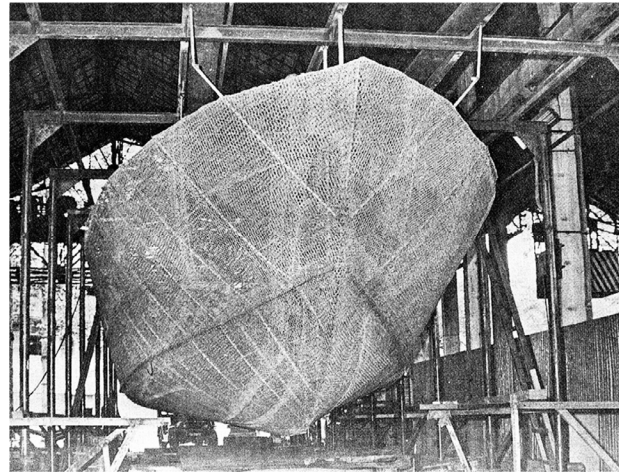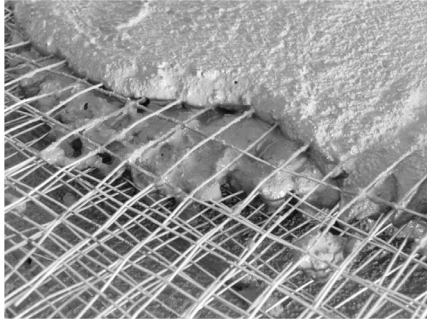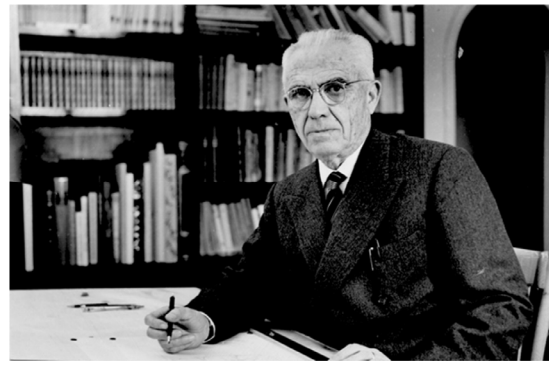


Ferrocement

- Pioneered by Nervi
- Dense, small gage reinforcement
- More flexible shapes – no formwork
- Well suited for thin shells
- Less cracking
- Low-tech applications



Palazzetto dello Sport, Rome, 1957. P.L. Nervi

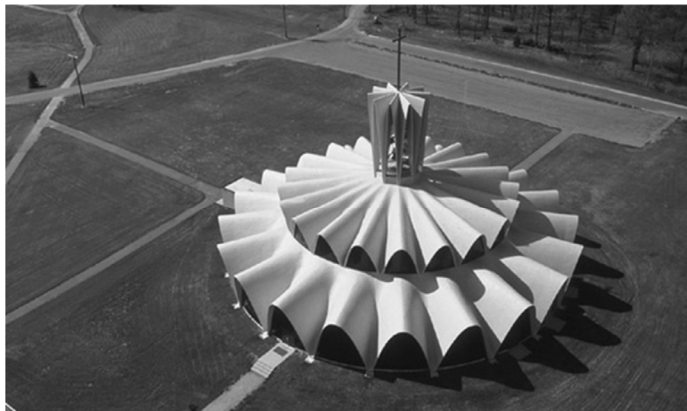

Priory Benedictine Church, Missouri, 1956. Architect Gyo Obata





Fiber Reinforced Concrete

Several different fiber types:

- Steel (SFRC)
- Glass (GFRC)
- Plastic e.g. polypropylene
- Carbon
- Organic e.g. bamboo

Better crack control
Secondary reinforcement

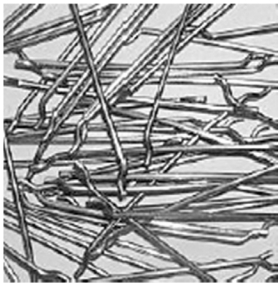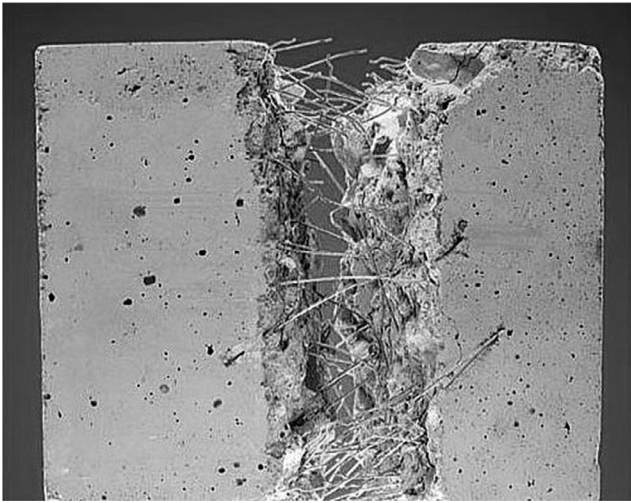

Single




Wave



Bundle

Glass Fiber Reinforced Concrete - GFRC

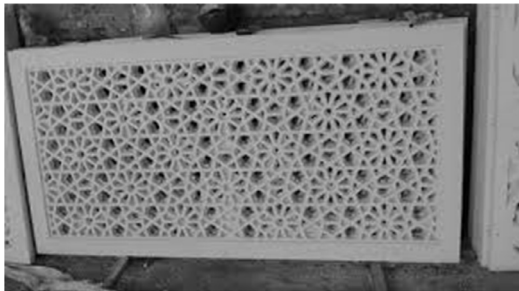

Carbon Fiber



University of Michigan, TCAUP

Bamboo




Structures II

Slide 49 of 51

Shotcrete

- Pneumatically applied
- High velocity
- Can include fiber
- Applied to backing
- Reinforced with bars
- Soil stabilization, tunnels

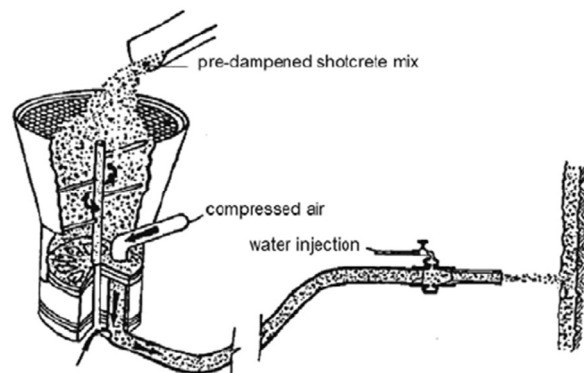

University of Michigan, TCAUP

Structures II

Slide 50 of 51

Textile Reinforced Concrete (TRC)

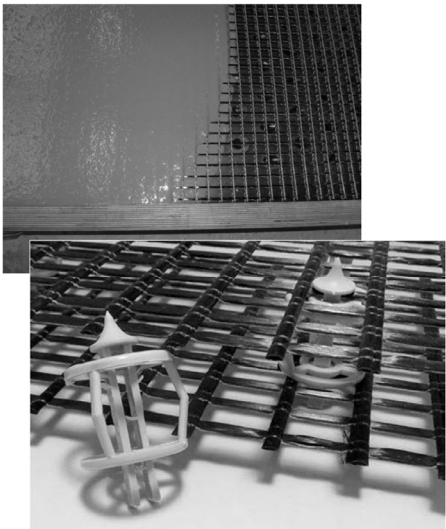


Figure 12: distTEX: special spacers for textile grids [photo: Frank Schladitz, TU Dresden]

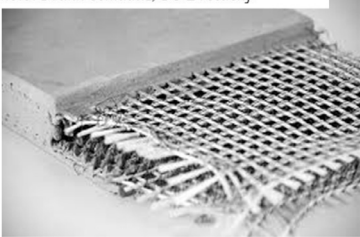


Figure 13: Manufacturing of the TRC hyper-shell layer by shotcrete [photo: © RWTH Aachen], [38]

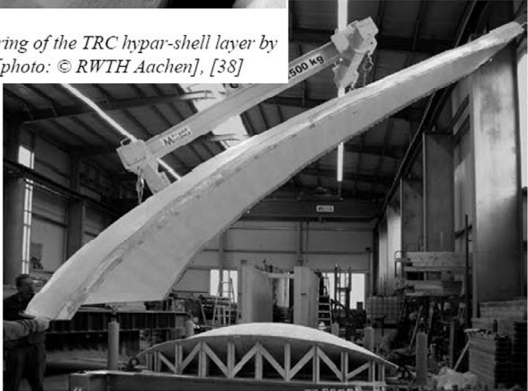


Figure 10: Demolding of a hardened shell element in the concrete yard in Kahla/Saxony [photo: Daniel Ehlig, TU Dresden]